

Research on Self-Propagating High-Temperature Synthesis of Ceramic Matrix Composites

Deshui Yu¹, Yan Zhang^{1,*}, Jianping Zhou¹, Daqian Sun², Hongmei Li²

¹School of Mechanical Engineering, Xinjiang University, Wulumuqi, China

²Key Laboratory of Automobile Materials, School of Materials Science and Engineering, Jilin University, Changchun, China

Email address:

yanzhang4967@163.com (Yan Zhang)

*Corresponding author

To cite this article:

Deshui Yu, Yan Zhang, Jianping Zhou, Daqian Sun, Hongmei Li. Research on Self-Propagating High-Temperature Synthesis of Ceramic Matrix Composites. *Engineering and Applied Sciences*. Vol. 8, No. 4, 2023, pp. 80-82. doi: 10.11648/j.eas.20230804.13

Received: July 17, 2023; Accepted: August 3, 2023; Published: August 22, 2023

Abstract: Ceramics have excellent properties such as high hardness, corrosion resistance, and wear resistance, and have great potential for applications in harsh environmental conditions. However, the hard and brittle nature of ceramics makes processing and modification very difficult, which requires its composites to form ceramic matrix composites with other materials with complementary performance advantages. Currently, ceramic composites are synthesized using brazing, diffusion welding and self-propagating high-temperature synthesis techniques. The residual thermal stresses in ceramic composites prepared by brazing and diffusion welding have a large impact on the mechanical properties of the joints, and self-propagating high-temperature synthesis can alleviate this drawback. Self-propagating high-temperature synthesis (SHS) technology is a technology that utilizes the high chemical reaction heat energy generated between the reactants to join the desired materials in a very short period of time, which can effectively alleviate the large residual stresses due to the differences in mechanical properties, such as coefficients of thermal expansion, between the parent materials. It has the advantages of simple synthesis process, simple equipment, low energy consumption, no external energy supply when the reaction occurs, and environmental pollution. This paper reviews the research progress of SHS technology in recent years in ceramic/metal dissimilar materials joining, and analyzes the micro-morphology and mechanical properties of ceramic/metal interfaces, and puts forward the advantages and disadvantages of SHS technology.

Keywords: Ceramic Matrix Composites, Mechanical Properties, SHS, Residual Thermal Stress

1. Introduction

Ceramic materials are characterized by good wear resistance, excellent corrosion resistance, as well as good thermal and chemical stability, and have important applications in aerospace, marine, and mechanical fields [1, 2]. However, ceramics are characterized by high brittleness, low ductility, and poor machinability, which makes it difficult to manufacture large and complex ceramic components, limiting their use in industry [3]. Metallic materials are commonly found in life and are widely used in modern industries. Steel is the most commonly used industrial metal material, possessing excellent toughness and strength, as well as weldability and processability [4]. However, stainless steel has a high specific gravity and is less resistant to corrosion and wear.

There are currently some challenges in achieving an effective connection between ceramics and steel [5]. The chemical properties of ceramics and steel are significantly different. Some conventional brazing materials, although they can wet the metal surface, have poor wettability for ceramic materials. The ceramic-steel connection interface is prone to the formation of a variety of complex brittle compounds such as oxides and carbides. These compounds are usually characterized by high hardness and brittleness, and the distribution at the interface is more complex, which can easily cause brittle fracture of the joint. The elastic modulus and thermal expansion coefficient of ceramic materials and steel are very different, and during the heating and cooling process, a large amount of residual stress is easily generated, which causes stress concentration at the interface between ceramic and metal joints and reduces the bonding strength of the joints.

2. Self-Propagating High-Temperature Synthesis

The self-propagation high-temperature synthesis method is a technique that uses the higher heat generated between reactants and by conduction to connect the base materials for reception welding. The filling material is changed during the joining process to form reaction products that can relieve large residual stresses due to differences in physical properties between the base materials [6]. S. F. Yu *et al.* [7] used Fe_2O_3 powders and Al powders as reaction materials, and then heated the reaction materials using a strong current to finally generate Al_2O_3 ceramics in situ on the upper

surface of stainless steel. As shown in Figure 1a, the stainless steel melted and formed a metallurgical bond with the ceramic, and the combined interface was tightly connected without defects such as pores and cracks. Al_2O_3 , α -ferrite and $\text{FeO-Al}_2\text{O}_3$ phases were found in the joint weld area. X. H. Hou *et al.* [8] achieved the high-temperature synthesis of Al_2O_3 ceramic-lined steel tubes by adding $\text{Na}_2\text{B}_4\text{O}_7$ to the $\text{Al-Fe}_2\text{O}_3\text{-Cr}_2\text{O}_3$ mixed feedstock. As shown in Figure 1b, the ceramic coating consisted of $\text{Al}_2\text{O}_3\text{-FeCr alloy-(Al}_{0.9}\text{Cr}_{0.1})_2\text{O}_3$ composite phase, and it was found that with the increase of $\text{Na}_2\text{B}_4\text{O}_7$ content, the residual Fe-Cr alloy particles in the ceramic coating increased and were uniformly distributed, forming a dense ceramic coating.

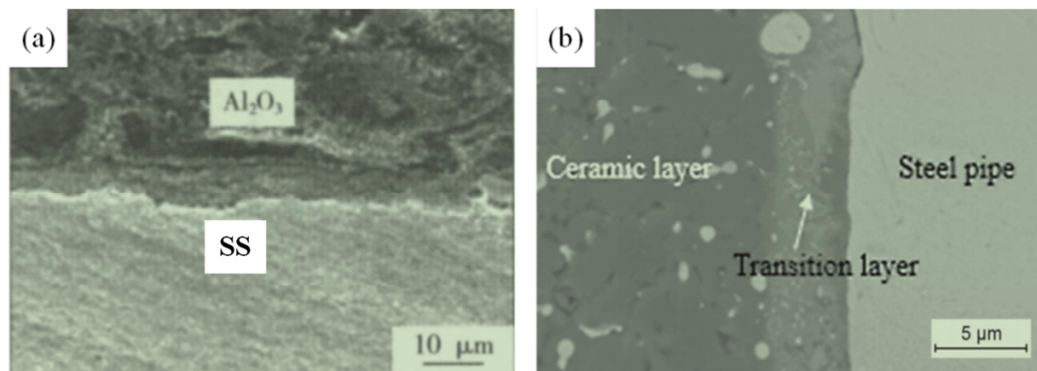


Figure 1. Self-propagating high-temperature synthesis: (a) $\text{Al}_2\text{O}_3/\text{Fe}_2\text{O}_3+\text{Al}$ powders/Steel. (b) $\text{Al}_2\text{O}_3/\text{Al-Fe}_2\text{O}_3\text{-Cr}_2\text{O}_3+\text{Na}_2\text{B}_4\text{O}_7$ /Steel.

Y [9] *et al.* prepared $\text{TiB}_2\text{-TiC}$ ceramic coatings using the self-spreading high temperature synthesis (SHS) technique to improve the hardness and wear resistance of Ti. The microhardness of $\text{TiB}_2\text{-TiC}$ ceramics was $2140 \text{ HV}_{0.5}$, and the wear rate was $5.5 \times 10^{-3} \text{ mm}^3 \text{ min}^{-1} \text{ N}^{-1}$ due to the ultra-low porosity and high strength TiB_2/TiC interface improves the mechanical properties. Liang [10] *et al.* investigated the SHS reaction behavior of the Cu - Ti - C system at different Cu contents. Cu also plays an important role in the ignition behavior of the SHS reaction. With the increase of Cu content, the combustion temperature decreases abruptly and the ignition time decreases and then increases. When the Cu addition was 20 wt.%, the ignition time of the system is the shortest. The SHS reaction involves two consecutive phases of combustion with different brightness intensities. These two combustion phases correspond to the formation of TixCu_y compounds and TiC particles, respectively. The SHS reaction products of the Cu - Ti - C system with different Cu contents consisted of TiC and Cu without an intermediate phase. Song [11] *et al.* prepared TiC particles in situ by a self-propagating high-temperature synthesis reaction and investigated the reaction behavior and generation pathways of TiC. It was shown that with the increase of Al content, the reaction temperature decreased and the size of TiC particles decreased significantly. The Al additive plays an important role in determining the size, morphology and formation pathway of TiC particles during SHS processing. Z [12] *et al.* prepared TiC/TiB_2 ceramic matrix composites by self-propagating high-temperature combustion synthesis and

pseudo-thermal isostatic pressing method using Ti, B4C and carbon powder as raw materials. The introductions of additional rod-like TiB_2 grains into the TiC/TiB_2 ceramics resulted in a significant increase in the fracture toughness of the dense materials synthesized by TC05 and TC06. Macedo [13] *et al.* synthesized $\text{Bi}_4\text{Ti}_3\text{O}_{12}$ ferroelectric ceramics by SHS technique and investigated the microstructure and electrical properties of $\text{Bi}_4\text{Ti}_3\text{O}_{12}$ ferroelectric ceramics. This study discusses the characterization of BIT ceramics produced by SHS, compares their microstructural and electrical properties with those of samples produced by conventional solid-state reactions, and concludes that the differences in conductivity and relative permittivity are attributed to differences in grain size and defect concentration. Miloserdov [14] *et al.* prepared, $\text{Al}_2\text{O}_3\text{-Cr}_2\text{O}_3 + \text{TiC}$ ceramic composites by SHS method using TiO_2 , Al and C powders as raw materials with the addition of Cr_3 and Al. The research on the mechanical properties of this material showed that this material seems to be promising to be used as a tool for machining high-strength steels with hardness up to 49 HRC. Nakashima [15] *et al.* successfully prepared Al_4SiC_4 high temperature resistant ceramics by SHS method using Si, Al and C as raw materials. It was found that Ar pressure is more suitable for the synthesis of Al_4SiC_4 because higher Ar pressure allows gaseous substances such as SiF_4 to be retained in the particle mixture and the reaction can be carried out stoichiometrically, and the Polytetrafluoroethylene additives promote the formation of silicon carbide. Furthermore, the oxide layer on the surface

of the silicon particles inhibits the reaction between silicon and carbon. Merz [16] et al. used an induction furnace-assisted SHS method for the rapid preparation of MAX-phase Mn_2AlB_2 ceramics from Al, Mn and B powders. The advantage of this method is the short synthesis time, which provides a unique solution for the large-scale preparation of MAB-phase powders.

3. Conclusion

Self-propagation high-temperature synthesis has the advantages of low energy consumption, high productivity, and low thermal effect on the base material. However, due to the fast reaction rate of self-propagation synthesis itself, the burning time of filler is difficult to control, thus leading to a complicated and difficult to control interfacial reaction.

References

- [1] Belmonte M. Advanced ceramic materials for high temperature applications [J]. *Advanced engineering materials*, 2006, 8 (8): 693-703.
- [2] Cho B R, Lee J J, Kang S K. Effect of composition change on sintering and metallizing of alumina ceramics [J]. *Journal of Ceramic Processing Research*, 2009, 10 (1): 121-123.
- [3] Donald I W, Mallinson P M, Metcalfe B L, et al. Recent developments in the preparation, characterization and applications of glass-and glass-ceramic-to-metal seals and coatings [J]. *Journal of Materials Science*, 2011, 46: 1975-2000.
- [4] Liu Y, Wang G, Cao W, et al. Brazing ZrB_2 -SiC ceramics to $\text{Ti}_6\text{Al}_4\text{V}$ alloy with TiCu-based amorphous filler [J]. *Journal of Manufacturing Processes*, 2017, 30: 516-522.
- [5] Li C, Si X, Dai X, et al. Understanding the effect of surface machining on the YSZ/ $\text{Ti}_6\text{Al}_4\text{V}$ joint via image based modeling [J]. *Scientific Reports*, 2019, 9 (1): 12027.
- [6] Ma D D. Self-propagating high-temperature synthesis of TiC/Fe cermet structural composites [J]. *Ceramics*, 2019 (07): 40-50.
- [7] Yu S F, Zhang Y Q, Xie M L, et al. Al_2O_3 ceramic/stainless steel self-propagating high temperature in-situ synthesis joining [J]. *Journal of Welding*, 2004 (02): 119-122+134.
- [8] Hou X H, Yu J K. Effect of $\text{Na}_2\text{B}_4\text{O}_7$ addition on the structure and properties of Al_2O_3 ceramic-lined steel pipe prepared by the GS-SHS method [J]. *Ceramics-Silikáty*, 2018, 62 (1): 74-80.
- [9] Bao Y, Huang L, An Q, et al. Insights into arc-assisted self-propagating high temperature synthesis of TiB_2 -TiC ceramic coating via wire-arc deposition [J]. *Journal of the European Ceramic Society*, 2020, 40 (13): 4381-4395.
- [10] Liang Y, Han Z, Lin Z, et al. Study on the reaction behavior of self-propagating high-temperature synthesis of TiC ceramic in the Cu-Ti-C system [J]. *International Journal of Refractory Metals and Hard Materials*, 2012, 35: 221-227.
- [11] Song M S, Huang B, Zhang M X, et al. Study of formation behavior of TiC ceramic obtained by self-propagating high-temperature synthesis from Al-Ti-C elemental powders [J]. *International Journal of Refractory Metals and Hard Materials*, 2009, 27 (3): 584-589.
- [12] Xinghong Z, Chuncheng Z, Wei Q, et al. Self-propagating high temperature combustion synthesis of TiC/ TiB_2 ceramic-matrix composites [J]. *Composites Science and Technology*, 2002, 62 (15): 2037-2041.
- [13] Macedo Z S, Ferrari C R, Hernandez A C. Impedance spectroscopy of $\text{Bi}_4\text{Ti}_3\text{O}_{12}$ ceramic produced by self-propagating high-temperature synthesis technique [J]. *Journal of the European Ceramic Society*, 2004, 24 (9): 2567-2574.
- [14] Miloserdov P A, Gorshkov V A, Andreev D E, et al. Metallothermic SHS of Al_2O_3 - Cr_2O_3 + TiC ceramic composite material [J]. *Ceramics International*, 2023, 49 (14): 24071-24076.
- [15] Nakashima Y, Kamiya R, Hyuga H, et al. Rapid fabrication of Al_4SiC_4 using a self-propagating high-temperature synthesis method [J]. *Ceramics International*, 2020, 46 (11): 19228-19231.
- [16] Merz J, Richardson P, Cuskelly D. Formation of Mn_2AlB_2 by induction-assisted self-propagating high-temperature synthesis [J]. *Open Ceramics*, 2021, 8: 100190.